

Length scale of dynamic heterogeneity in polymer nanocomposites.

S. Srivastava, A. K. Kandar, J. K. Basu, M.K. Mukhopadhyay, L. B. Lurio, S. Narayanan and S.K. Sinha.

Department of Physics, Indian Institute of Science, Bangalore, 560012, India

Department of Physics, University of California San Diego, La Jolla, CA 92093, USA,

Department of Physics, Northern Illinois University, De Kalb, IL 60115 USA,

Advanced Photon Source, Argonne National Laboratory, Argonne, IL 60439, USA.

September 30, 2008

Abstract

Using X-ray photon correlation spectroscopy measurements on gold nanoparticles embedded in polymethylmethacrylate we provide evidence for existence of an intrinsic length scale for dynamic heterogeneity in polymer nanocomposites similar to that in other soft materials. We also show how the dynamics varies in a complex way with various parameters.

Polymer nanocomposites (PNC) are a novel class of multifunctional hybrid materials which are obtained by appropriate mixing of nanoparticles and polymers leading to a wide range of applications in terms of their unique electrical, optical, and thermo-mechanical properties [1 - 4]. They also belong to this new class of materials, under the umbrella of soft glassy materials, which exhibit rich and complex thermal, mechanical and rheological behavior [5 - 11]. Extensive experimental work has been performed over the decade or so on studying the modifications of thermal and mechanical properties imparted to the matrix polymer by addition of nanoparticles of various shapes and sizes [4,12-15]. Numerical simulations and theoretical calculations have started to emerge in the meanwhile to provide some insight and understanding into the static structure and phase behavior in various model nanoparticle - polymer hybrid systems [16-20]. Homogeneous dispersion of nanoparticles in polymer matrices is a major obstacle [3] towards the ultimate goal of obtaining high performance materials. In this respect it has been observed by us [4] and a few other groups [21] that using a polymer capped nanoparticle in a matrix of chemically matched homopolymer matrix is a very effective way of ensuring homogeneous dispersion. However, the theory and simulations for the static structure and phase behavior for such systems are only just beginning to emerge [16-20] and a microscopic theory to treat the dynamics, of both polymer capped and uncapped nanoparticles in polymer matrices, including viscoelasticity, glass formation or diffusion of nanoparticles does not exist. Dynamics of soft glassy materials is extremely rich and complex [5,7,22-24]. Depending on various parameters like volume fraction, (ϕ) and temperature, (T) such systems exhibit complex slow dynamics characteristic, of glassy or jammed phase [5,7, 22-24]. Dynamic heterogeneity is a key feature of such systems and evidence of length scale dependent dynamic heterogeneity has been observed in simulations [10,25-26]and certain experiments [27, 28]. In this communication we provide evidence for existence of a length scale of dynamic heterogeneity for PNC. We also provide the first glimpse of the complexity and richness of phase behavior in dynamics of polymer nanocomposites as a function of ϕ , T and the wave vector, q , through detailed synchrotron multi-speckle x-ray photon correlation spectroscopy (XPCS) measurements.

In XPCS one measures the intensity autocorrelation function [9,11,14,29],

$$g_2(q, t) = 1 + b|f(q, t)|^2. \quad (1)$$

Here, $f(q, t)$ is the intermediate scattering function (ISF), b is the speckle contrast and t is the delay time. We have used ISF of general form,

$$f(q, t) = \exp - (t/\tau)^\beta, \quad (2)$$

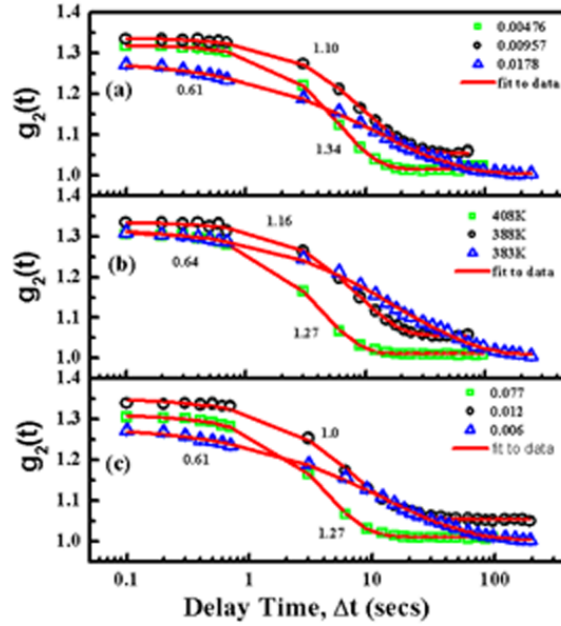


Figure 1: $g_2(t)$ vs t showing cross over in β values with respect to (a) Wave vector, q (b) Temperature, T and (c) Volume fraction, ϕ for samples A , B and C. The relaxations not only show simple exponential ($\circ$) decay but compressed ($\square$) and stretched ($\triangle$) exponential decay as well. Solid line are fits with eqn. 1 . Number indicated side by are the β values extracted from the fits.

where τ and β represents the characteristic relaxation time of the system and the Kohlrausch exponent respectively. The mean relaxation time τ follows a power law behavior and is given by

$$\tau \propto q^{-\alpha}. \quad (3)$$

For diffusive motion, $\alpha = 2$. However, for ballistic or super-diffusive motion α is predicted to be ~ 1 and for sub diffusive motion $\alpha > 2$ [30]. Normally , β is independent of q , however there has been some recent observation in colloidal gel systems where β has also been found to depend on q . However the underlying physics is not clear. We performed XPCS measurements at 8-ID beamline of the Advance Photon Source with partially coherent X-rays of energy 7.35 KeV of beam size $20\mu\text{m} \times 20\mu\text{m}$ using a CCD (Princeton Instruments). The total exposure time at each sample position was limited to ~ 10 minutes to minimize radiation damage. The results of XPCS measurements, presented here, are based on three different samples (A,B,C), of gold nanoparticles capped with Polymethylmethacrylate (PMMA, 120K , sigma aldrich) and embedded in PMMA matrix, prepared by a method described earlier [4]. All samples were annealed at 150°C for 24–30 hrs under a vacuum of 5×10^{-4} mbar. Sample A consists of gold nanoparticles of mean diameter, d , 5 nm embedded in PMMA matrix with volume fraction ($\phi = 0.006$) corresponding to a mean interparticle spacing , $h \sim 196 \text{ \AA}$. The glass transition temperature , (T_g), for this sample as measured using modulated differential scanning calorimetry, was found to be 392 K . Similarly for sample B, d is 6 nm, $h \sim 180 \text{ \AA}$, $\phi = 0.012$ and $T_g \sim 380$ K. Sample , C is embedded with nanoparticle of diameter 10 nm , with $h \sim 105 \text{ \AA}$, $\phi = 0.077$ and $T_g \sim 381$ K. Fig.1 shows the rich and complex dependence of dynamics in such nanocomposites on various parameter like volume fraction, temperature and crucially the wave vector of measurement and hence the length scale. Since x-rays are mostly sensitive to the scattering contrast between gold nanoparticle and PMMA , the observed dynamics is mostly a reflection of the motion of the PMMA capped gold nanoparticles through the background of matrix PMMA and is essentially sensitive to the length scale dependent viscoelastic property of the medium. It is clear that the relaxations evolve as a fraction of the various parameters ϕ , T and q for all the samples and shows stretched - compressed cross over as has been observed for some other soft matter samples [11,25].

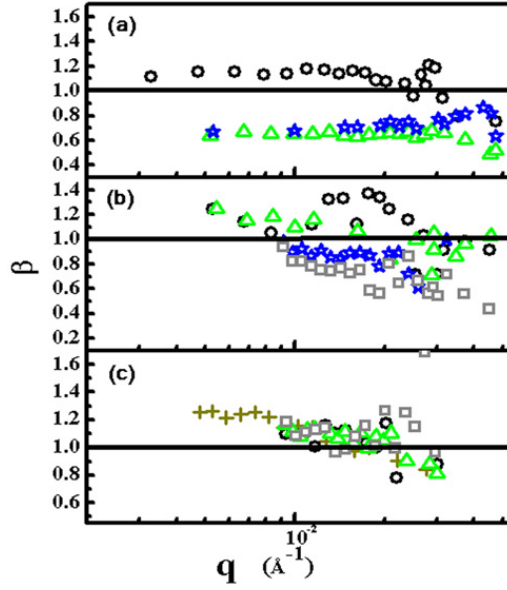


Figure 2: β vs q at various temperatures for samples, A, B, C shown in panel a, b, c respectively . The respective temperatures are (+ - 408K, o - 398K, Δ - 388K, $\star$ - 383K, $\square$ - 378K).

However much better insight about complexity of the dynamics is obtained by looking at the dependence of the β and τ , extracted using eqn .2 on these parameters. In Fig. 2 we show how the obtained exponent , β ,for various samples at different respective measured temperatures vary as a function of wave vector q . Let us first discuss the low q behavior of β observed in our samples. Clearly , for sample A , the relaxation is highly stretched , for measured temperatures, T , below the thermodynamical glass transition temperature , T_g , as expected. However for $T > T_g$ we find the ubiquitous $\beta > 1$ behavior indicative of anomalous diffusion typical of slow relaxation in soft and granular materials undergoing jamming transition [5, 7, 10-11, 22-24, 27-28].

On the other hand, for sample C, β shows a clear wave vector dependent behavior. At low q , $\beta > 1$ for all measured temperatures , including that below its , T_g , indicating that the dynamics in this system is dominated by viscoelasticity of the effective medium due to the surrounding particles and polymers . This behavior has remarkably similarity to the predicted behavior by Bouchaud et al [23]. Interestingly sample B, which has intermediate volume fraction clearly shows evolution in terms of the relaxation spectra as a function of measured temperature . Specifically , at low q , ($q \leq 0.02 \text{ \AA}^{-1}$) $\beta \leq 1$ for $T \leq T_g$ while $\beta > 1$ for $T > T_g$. The value of β are closer to 1 for $T \leq T_g$ for sample B than it is for sample A and also increases with temperature. Thus the dynamics in such systems is intermediate between that of sample A and B and the intimate relation of T and ϕ in determining the dynamics of PNC is vividly demonstrated here. At higher q ($q \geq 0.02 \text{ \AA}^{-1}$, $\beta \sim 1$ for all T and ϕ , except for the case of sample A at $T < T_g$. The cross over from $\beta \sim 1$ to $\beta >$ and < 1 takes place at wave vector , q_c . The temperature dependent cross - over in β is opposite to what has been observed recently [11] and indicates fundamentally different dynamics as compared to nanoparticles in molecular supercooled fluids. The cross over in β for $q < q_c$ as a function of temperature (for sample A and B) can be understood as a cross - over from polymer dominated dynamics at low temperatures (below T_g of PMMA = 388 K) to particle dominated dynamics at $T > T_g$. However deeper insight can be obtained from Fig. 3 which quantifies the wave vector dependence of relaxation time τ , and delineates the nature of microscopic diffusion in our PNC system. We find that similar to β , α also shows a cross over length scale , corresponding to $q_c \sim 0.02 \text{ \AA}^{-1}$. For $q > q_c$ we find that $1 \leq \alpha \leq 2$ depending on T and ϕ of nanoparticles, whereas for $q < q_c$, $0 < \alpha < 1$. This is shown in Fig. 4(a) for all our samples and at all measured temperatures . This low wave vector behavior, coupled with non - exponential relaxation indicates onset of a form of dynamic heterogeneity in the PNC systems. If we define $l_c \propto 1/q_c$ as a length scale corresponding to the cross - over wave vector then this provides an estimate of the smallest region in the system where dynamics is spatially heterogeneous. For sample C we observe that this length scale increases slightly ($q_c \sim 0.01 \text{ \AA}^{-1}$).

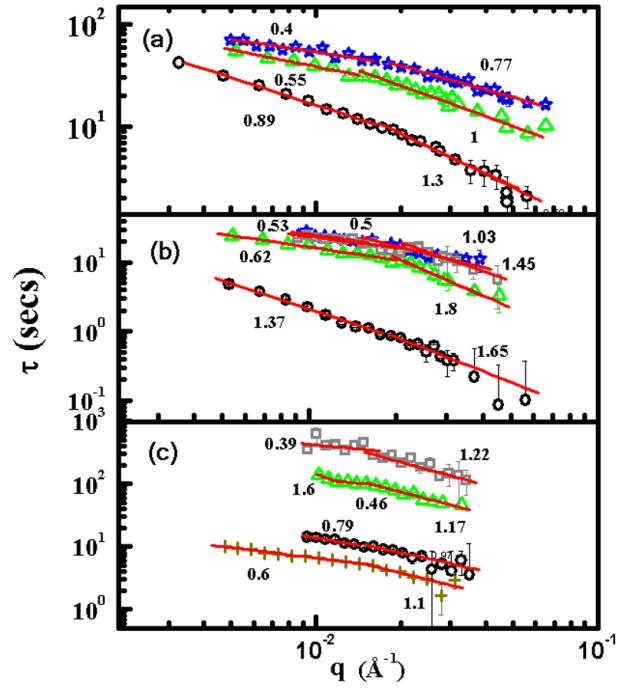


Figure 3: Relaxation time τ , vs q for samples A, B, C in panel a, b, c respectively, at different temperatures (+ - 408K, o - 398K, Δ - 388K, $\star$ - 383K, $\square$ - 378K). The straight lines are linear fits to the data used to estimate α , indicated along side each curve according to eqn. 3

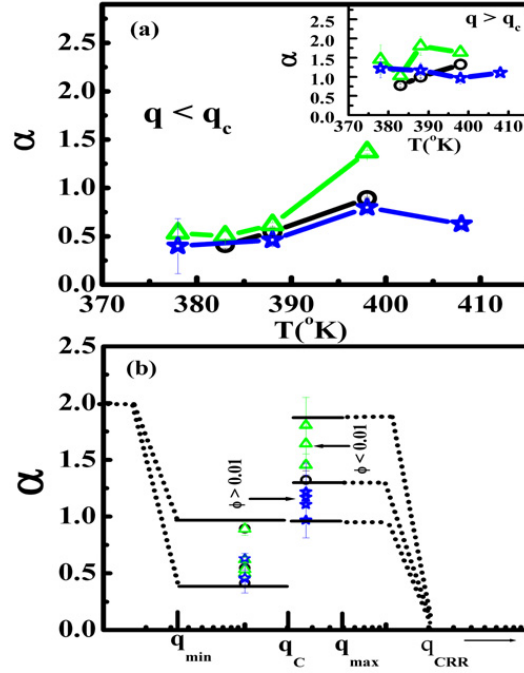


Figure 4: (a): α vs T , obtained from linear fits in fig. 3 for different samples A ($\circ$), B (Δ), C ($\star$), for $q < q_c$. Inset shows α vs T for $q > q_c$ for three samples, A, B and C (symbols defined above). (b): Schematic of our model for variation of α within certain wave vector ranges as defined in text. q_{max} is the highest measured q in our data. The solid lines defines the band of α values within our measured q range $q_{min} < q < q_{max}$ while dotted lines represent expected behavior outside this range. α lies mostly within 1 in the band $q_{min} < q < q_c$ and $1 \leq \alpha < 2$ for $q_c < q < q_{max}$. The dotted line beyond q_{max} indicates projected variations of α with q ($\alpha \rightarrow 0$, $q \rightarrow q_{CRR}$) for supercooled liquids (ref 31, 32) near and below T_g .

Our measurements extends only upto $q \sim 0.005 \text{ \AA}^{-1}$ and hence $l_{max} \propto 1/q_{min}$ provides an estimate of the largest size of such domains. It might be noted here that qualitatively similar behavior of length scale dependent relaxation was also observed in recent molecular dynamic simulation of colloidal gels and a similar length scale was identified at where there is a cross over in the dynamics[25]. This implies that the exponent α is not a constant over the entire q range. This fact is highlighted in Fig. 4(b) where we have identified various regions in q space and the corresponding values α could take which includes regions within our measured range ($q_{min} < q < q_{max}$) and outside (refer caption). The existence of the hydrodynamic region with $\alpha = 2$ can be conjectured to exist at wave vectors smaller than our q_{min} . It might be interesting to note that for one of our data (sample C, $T = 388\text{K}$), we clearly see three regions for α including a region at low q where $\alpha \sim 1.6$ indicative of the above mentioned onset of hydrodynamic region. It has been observed that [31-32] an intrinsic length scale for a supercooled liquid corresponding to onset of dynamic heterogeneity l_{CRR} exists below which diffusion is anomalous and $\alpha \rightarrow 0$, while above it normal diffusion with $\alpha \rightarrow 2$ exists. Depending on the temperature and especially near and below T_g there is an intermediate region where α takes on values between 0 and 2 [25, 31 - 32]. It is reasonable to assume that $l_{CRR} \sim \xi_{CRR}$, which for our PNC has been measured to be $\sim 25 \text{ \AA}$ [4]. This corresponds to a q_{CRR} of $\sim 0.3 \text{ \AA}^{-1}$ which is not reachable in a typical XPCS measurements. In our case $q_{CRR} \gg q_{max}$ (refer caption). Hence the values of $\alpha \rightarrow 2$ for $q > q_c$ corresponds to this region ($q_c < q < q_{CRR}$) for the polymer glass. For our PNC system $\alpha < 2$ for $q > q_c$ since particle induced jamming is prevalent. For the highest ϕ , we have used for our measurements, this jamming effect increases to such an extent that the cross over in dynamics is not clearly observed within the measurable q range (Fig. 3(c) and Fig. 4(b)). Clearly our systems not only exhibit some of the conventional phases found in other related soft and glassy systems but exhibits new phases in dynamics which, to our knowledge, has not been found earlier. The above discussion can be summarised by identifying different regions in

the $T - \phi - q$ parameter space in which our PNC shows distinct dynamical behavior. In Phase *I* the dynamics is typical of that observed in jammed systems and in soft glassy matter, in general, and is characterised by a compressed exponential relaxation and hyper - diffusive motion ($\alpha \sim 1$). This type of dynamics is seen mostly at $T > T_g$ and $q < q_c$ for sample A and B, which have relatively low volume fraction of gold nanoparticles. In Phase *II* the dynamics is unusual since $\beta > 1$ and $\alpha < 1$. This phase is only seen for sample C, with the highest volume fraction of our samples, at all temperatures and indicates that the dynamics is dominated by particles induced jammed behavior. The diffusion is highly anomalous with weak wave vector dependence of relaxation indicating heterogeneous dynamics mainly due to particle jamming. Phase *III* with $\beta \sim 1$ and $\alpha > 1$ is seen for $q > q_c$ and $T > T_g$ and is indicative of liquid like behavior, as expected. Phase *IV* ($\beta < 1$ and $\alpha > 1$) occurs for sample A and B for $q > q_c$ and $T < T_g$. As explained earlier, this is the phase which would have been the hydrodynamic region ($\tau \propto 1/q^2$ for $q < q_{CRR}$). However the onset of the additional dynamic heterogeneity in PNC truncates this region to within $q_c < q < q_{CRR}$. It is possible that the measurements at temperatures $T \gg T_g$ would ultimately reveal the $1/q^2$ diffusive dynamics as revealed in various other measurements [11,25]. Finally, in Phase *V*, $\beta < 1$ and $\alpha < 1$ which occurs for sample A and B for $T < T_g$ and $q < q_c$. The dynamics in this phase is dominated mostly by polymer visco-elasticity but the heterogeneity in dynamics is intrinsic to the PNC system due to the creation of domain of size $l_{min} < l < l_c$. We have presented systematic studies of dynamics in typical PNC system consisting of PMMA capped gold nanoparticles embedded in PMMA matrix of identical molecular weight with various volume fractions. Our temperature and wave vector dependent XPCS measurements provides new insight into the fascinating dynamics in these systems and for the first time reveals the existence of a dynamical heterogeneity length scale intrinsic to PNC systems. The phase behavior in such systems is more complex and interesting and requires extensive investigation to fully understand the physics at the microscopic scale leading to such diverse and puzzling behavior.

The authors acknowledge M. Sprung (APS) for discussions and A. Sandy (APS) for assistance in experiments. This work benefitted by the use of facilities at APS, which is supported by U.S. DOE (BES) under Contract No. W - 31 - 109 - Eng - 38 to the University of Chicago. Part of the work has been supported by DST, India and UCSD.

References

- [1] R. B. Thompson, V. V. Ginzburg, M. W. Matsen, A. C. Balazs, *Science* **292**, 2469 (2001).
- [2] M. E. Mackay et al, *Science* **311**, 1740 (2006).
- [3] A. C. Balazs, T. Emrick, T. P. Russell, *Science* **314**, 1107 (2006).
- [4] S. Srivastava, J. K. Basu, *Phys. Rev. Lett.* **98**, 165701 (2007).
- [5] L. Cipolletti, L. Ramos, *J. Phys.: Condens. Matter* **17**, R253 (2005).
- [6] P. Sollich, F. Lequeux, P. Hebraud, M. E. Cates, *Phys. Rev. Lett.* **78**, 2020 (1997).
- [7] A. S. Keys, A. R. Abate, S. C. Glotzer, D. J. Durian, *Nature Phys.* **3**, 260 (2007).
- [8] K. Statford, R. Adhikari, I. Pagonabarraga, J.C. Desplat, M. E. Cates, *Science* **309**, 2198 (2005).
- [9] B. Chung et al, *Phys. Rev. Lett.* **96**, 228301 (2006).
- [10] P. Chaudhuri, L. Berthier, W. Kob, *Phys. Rev. Lett.* **99**, 060604 (2007).
- [11] C. Caronna, Y. Chushkin, A. Madsen, A. Cupane, *Phys. Rev. Lett.* **100**, 055702 (2008).
- [12] A. Bansal et al, *Nature Materials* **4**, 693 (2005).
- [13] P. Rittigstein, R. D. Priestley, L. J. Broadbelt, J. M. Torkelson, *Nature Materials* **6**, 278 (2007).
- [14] R. AravindaNarayanan et al, *Phys. Rev. Lett.* **97**, 075505 (2006).
- [15] R. Krishnamoorti, R. A. Vaia, *J. Polymer Science Part B: Polymer Physics* **45**, 3252 (2007).
- [16] S. Sen, J. D. Thomin, S. K. Kumar, P. Keblinski, *Macromolecules* **40**, 4059 (2007).
- [17] S. E. Harton, S. K. Kumar, *J. Polymer Science Part B: Polymer Physics* **46**, 351 (2008).
- [18] J. B. Hooper, K. S. Schweizer, *Macromolecules* **40**, 6998 (2007).
- [19] G. J. Pakonstantopoulos, M. Doxastakis, P. F. Nealey, J. L. Barrat and J. J. de Pablo, *Phys. Rev. E* **75**, 031803 (2007).

- [20] V. Pryamitsyn, V. Ganesan , *Macromolecules* **39**, 844 (2006).
- [21] A. Bansal et al , *J. Polymer Science Part B: Polymer Physics* **44**, 2944 (2006).
- [22] L. Cipelletti, S. Manley, R. C. Ball, D. A. Weitz , *Phys. Rev. Lett.* **84**, 2275 (2000).
- [23] J. P. Bouchaud, E. Pitard , *Eur. Phys. J. E.* **6**, 231 (2001).
- [24] V. Trappe , V. Prasad, L. Cipelletti, P. N. Segre , D. A. Weitz, *Nature* **411**, 772 (2001).
- [25] E. DelGado, W. Kob , *Phys. Rev. Lett.* **98**, 028303 (2007).
- [26] P. I. Hurtado , L. Berthier, W. Kob , *Phys. Rev. Lett.* **98**, 135503 (2007).
- [27] A. Duri , L. Cipelletti , *Europhys. Lett.* **76**, 972 (2006).
- [28] V. Trappe et al , *Phys. Rev. E*, **76**, 051404 (2007).
- [29] H. Kim et al , *Phys. Rev. Lett.* **90**, 068302 (2003).
- [30] R. Metzler , J. Klafter, *Phys. Reports* **339**, 1 (2000).
- [31] D. A. Stariolo , G. Fabricius, *J. Chem. Phys.* **125**, 064505 (2006).
- [32] L. Berthier, D. Chandler, J. P. Garrahan, *Eurphys. Lett.* **69** , 320 (2005).